

HOSTED BY



ELSEVIER

Contents lists available at ScienceDirect

## Journal of King Saud University – Science

journal homepage: [www.sciencedirect.com](http://www.sciencedirect.com)

Original article

Synthesis and antimicrobial activity of silver nanoparticles: Incorporated *couroupita guianensis* flower petal extract for biomedical applicationsS. Logambal<sup>a</sup>, T. Thilagavathi<sup>b</sup>, M. Chandrasekar<sup>c</sup>, C. Inmozhi<sup>d</sup>, Philippe Belle Ebanda Kedi<sup>e</sup>, F.A. Bassyouni<sup>f</sup>, R. Uthrakumar<sup>a,\*</sup>, Azhaguchamy Muthukumaran<sup>g</sup>, Suresh Naveenkumar<sup>g</sup>, K. Kaviyarasu<sup>h,i,\*</sup><sup>a</sup> Department of Physics, Government Arts College (Autonomous), Salem 636007, Tamil Nadu, India<sup>b</sup> Department of Physics, Government College for Women (Autonomous), Kumbakonam 612001, Tamil Nadu, India<sup>c</sup> Department of Physics, TAG. Govt. Arts College, Tindivanam 604307, Tamil Nadu, India<sup>d</sup> Department of Physics, Government Arts College for Women, Salem 636008, Tamil Nadu, India<sup>e</sup> Department of Animal Biology and Physiology, Faculty of Science, University of Douala, P.O. Box 24157, Douala, Cameroon<sup>f</sup> Chemistry of Natural and Microbial Products Department, National Research Center, 12622 Cairo, Egypt<sup>g</sup> Department of Biotechnology, Kalasalingam Academy of Research and Education, Krishnankoil, Tamil Nadu, India<sup>h</sup> UNESCO-UNISA Africa Chair in Nanosciences/Nanotechnology Laboratories, College of Graduate Studies, University of South Africa (UNISA), Muckleneuk Ridge, PO Box 392, Pretoria, South Africa<sup>i</sup> Nanosciences African Network (NANOAFNET), Materials Research Group (MRG), iThemba LABS-National Research Foundation (NRF), 1 Old Faure Road, 7129, PO Box 722, Somerset West, Western Cape Province, South Africa

## ARTICLE INFO

## Article history:

Received 11 June 2022

Revised 21 October 2022

Accepted 14 November 2022

Available online 17 November 2022

## Keywords:

*Couroupita guianensis* flower petals

Silver nanoparticles

X-ray

DSL analysis

Antimicrobial activity

Photocatalytic activity

## ABSTRACT

Recently, numerous plant-based synthesis techniques have been used to develop metal nanoparticles. The current study uses the medicinal plant extract of *couroupita guianensis* (CG) petals to create biogenic silver nanoparticles in an environmentally friendly manner. Different techniques, including ultraviolet-visible spectroscopy (UV-vis), Fourier Transformation Infrared spectroscopy (FTIR), X-ray diffraction (XRD), and Dynamic Light Scattering (DLS) analysis, are used to evaluate synthesized silver nanoparticles. From the XRD results confirm the emergence of nanosilver crystalline arrangement with the characteristic peaks at the glancing angles of 38.04°, 44.22°, 64.40°, and 77.37°. UV-vis spectroscopy displays the spectral absorption at  $\lambda^{\text{max}} = 282$  nm and shows the formation of silver nanoparticles. Images of produced Ag NPs taken with a scanning electron microscope (SEM) show the creation of flower-shaped particles. The functional behavior of flavones, triterpenoids, and polyphenols belonging to *couroupita guianensis* has been observed by ensuring their selective absorptions in FTIR spectral analysis silver nanoparticles had a substantial antibacterial effect on Gram-positive (*B. subtilis*) and Gram-negative (*Escherichia coli*) bacteria in general. It is found to become effective when symbiotic with the extract of *couroupita guianensis* flower petals for enhancing their antibacterial properties. This composite product gives a new and cost-effective formulation with more therapeutic possibilities. The observed results wide open the avenues of research possibilities with a lot of future scopes. The photocatalytic degradation efficiency of CG-Ag NPs on methylene blue (MB) dye was evaluated under visible light irradiation and produced indications of the synthesized material for photocatalytic applications.

© 2022 The Authors. Published by Elsevier B.V. on behalf of King Saud University. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

\* Corresponding authors at: UNESCO-UNISA Africa Chair in Nanosciences/Nanotechnology Laboratories, College of Graduate Studies, University of South Africa (UNISA), Muckleneuk Ridge, PO Box 392, Pretoria, South Africa (K. Kaviyarasu).

E-mail addresses: [philippe\\_belle@yahoo.fr](mailto:philippe_belle@yahoo.fr) (P. Belle Ebanda Kedi), [uthraloyola@yahoo.com](mailto:uthraloyola@yahoo.com) (R. Uthrakumar), [kavi@tlabs.ac.za](mailto:kavi@tlabs.ac.za) (K. Kaviyarasu).

Peer review under responsibility of King Saud University.



Production and hosting by Elsevier

## 1. Introduction

Medicinal plants are special elements known for their therapeutic scope and render long-time remedies for several human diseases. It is mainly because of the healing value of their components used as a raw material in modern medicine. The *couroupita guianensis* (CG) is a tree and its parts are familiar components used for medicinal purposes. Particularly, its chemical ingredients are responsible for various pharmacological and therapeutic properties. The study used to explore the characteristic

<https://doi.org/10.1016/j.jksus.2022.102455>

1018-3647/© 2022 The Authors. Published by Elsevier B.V. on behalf of King Saud University.

This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

features of *Couroupita guianensis* is essentially required to prove its potential in clinical applications. Under the discipline of materials science, the nanomaterial is a fast-growing area that renders various types of materials find application in a wide variety of fields including medical, chemical, catalytic, mechanical, electronic, and environmental industries (Alexandra et al., 2018; Krishna and Singara, 2016; Senthil et al., 2019; Tatiane et al., 2020). Various synthesis routes are available to produce nanomaterials employing physical, chemical, and biological methods (Katta and Dubey, 2020; Kseniya et al., 2020; Vijay et al., 2019). Nanomaterial synthesis also causes adverse effects producing environmental (or) pollution-related issues. Nanotechnology also supports rectifying these pollution-related issues with nanoscale materials of various types. The application potential of nanomaterials is wide in clinical issues in the field of biomedical. Silver nanoparticle (Ag NPs) is one of the elements proven their biological characteristic for many clinical issues. The use of biological sources such as bacteria, fungi, algae, and plants in the green production of silver nanoparticles is one of the most promising ways. Previous studies have shown that leaf (Panimalar et al., 2022), flower buds (Lakshmanan et al., 2018), fruit (Aarti et al., 2017), stem (Saddaf et al., 2019), root (Fuad et al., 2019), and flower extracts are inadequate biological approaches for producing AgNPs (Periasamy et al., 2019; Nayanmoni et al., 2015; Shangpeng et al., 2019; Renuka et al., 2020; Kumar et al., 2011; Gousia et al., 2013). It is generally suggested that the synthesis of silver nanoparticles using plant materials is a promising, profitable method easy to scale. In the present work, the extract of a medical plant from the family of Lecythidaceae namely, *Couroupita guianensis* is symbiotic with the silver nanoparticle for biomedical applications. Fig. 1 displays the floral flakes of *Couroupita guianensis* colored with yellow, red, and pink in stunning scenic color. Widely used medicinal plants in India have indicated a broad spectrum of antimicrobial and antifungal activities. The flowers of *Couroupita guianensis* have signified sufficient antioxidant activity. The phenolic compound of petals is active in the treatment of renal and stomach problems and has anti-inflammatory effects (Logambal et al., 2022).

The biological function of flavonoids, in addition to their antioxidants, includes protection against allergies, inflammation, platelet aggregation, microorganisms, ulcerates, hematoxylin, viruses, and tumors. Isatin is one of the effective components of the medicinal plant *Couroupita guianensis*, known well for its cytotoxic action contrary to certain lines of tumor cells and it is found to be a potential source of new chemotherapy agents. It is used to treat hypertension, tumors, pain, inflammatory processes, cold, stomachache



Fig. 1. *Couroupita guianensis* flower petal.

(norovirus), skin diseases, malaria (rotavirus), wounds and toothache (Panimalar et al., 2020). *E. coli* and *Bacillus subtilis* strains, as well as the effect of AgNPs on the growth of both bacterial, it was a very effective inhibitor of *E. coli* and *B. subtilis* growth (Chandrasekar et al., 2022). The present study aimed to synthesize silver nanoparticles from aqueous extracts of petals of the medicinal plant *Couroupita guianensis*. The characterization has been summed up using various techniques used for assessing their size, morphological characteristics, and antimicrobial activity. In the current work, we have chosen *Couroupita guianensis* dopant for silver nanoparticles (AgNPs) to improve photocatalytic performance. Antibacterial, optical, thermal, and catalytic characteristics of silver NPs are all controlled by their size and form. Ag is an excellent conductor with a decent bandgap and optical properties. The addition of CG to AgNPs will affect their antibacterial properties as well as the rate of electron-hole pair recombination. The report discusses visible-light-induced improved photocatalytic degradation utilizing CG doped AgNPs catalyst produced using the sol-gel method (Brajesh et al., 2016; Gupta et al., 2012).

## 2. Materials and procedure

### 2.1. Plant material sampling and identification

Raw chemicals of analytical grade (AR) with a purity of  $\geq 99\%$  of silver nitrate have been purchased from E-Merk life science private limited, Mumbai, India. The fresh and healthy petals of the *Couroupita guianensis* flowers were collected around the fertile land located in Salem, Tamil Nadu, India. Following schematic procedures like washing, and sterilizing used to remove impurities from the fresh floral flakes facilitates the preparation of the flower petals suitable to collect the extract.

### 2.2. Preparation of flower petal extract

The washed floral flakes were dried and 5 gm weighted flakes were immersed in 50 ml distilled water taken in 100 ml beaker and boiled for 20 min. After boiling, the extract was cooled and filtered using a Whatman No 1 filter paper and filter paper (size 0.4 m) in a sequence to create a final extract, which was then stored at 4 °C.

### 2.3. Silver nanoparticle synthesis

In a conical flask, 50 ml of 1 mM aqueous silver nitrate was combined with 5 ml of floral flake extract. The solution mixture has been stirred vigorously in a magnetic stirrer for 15 min. The process lasts for 30 min and until the silver ions are reduced to silver particles at room temperature. The hue of the reaction mixture shifted from blue green to brown after 30 min, according to the researchers. It shows that the UV-visible spectrophotometer can guarantee the reduction of silver ions into AgNPs.

## 3. Results and discussion

### 3.1. X-ray diffraction analysis

Observed X-ray powder diffraction (XRD) results recorded the details of the crystal lattice and the structure of the synthesized AgNPs as given in Fig. 2(a). The X-ray diffractogram evident the emergence of diffraction peaks at the glancing angles ( $2\theta$ ) 38.04°, 44.22°, 64.40°, and 77.37° which parallel to the planes of the cubic structures of silver nanoparticles (111), (200), (220), and (311). As reported elsewhere (Wong and Tie, 1995), the observed peaks and their glancing angles are agreed well with the previous

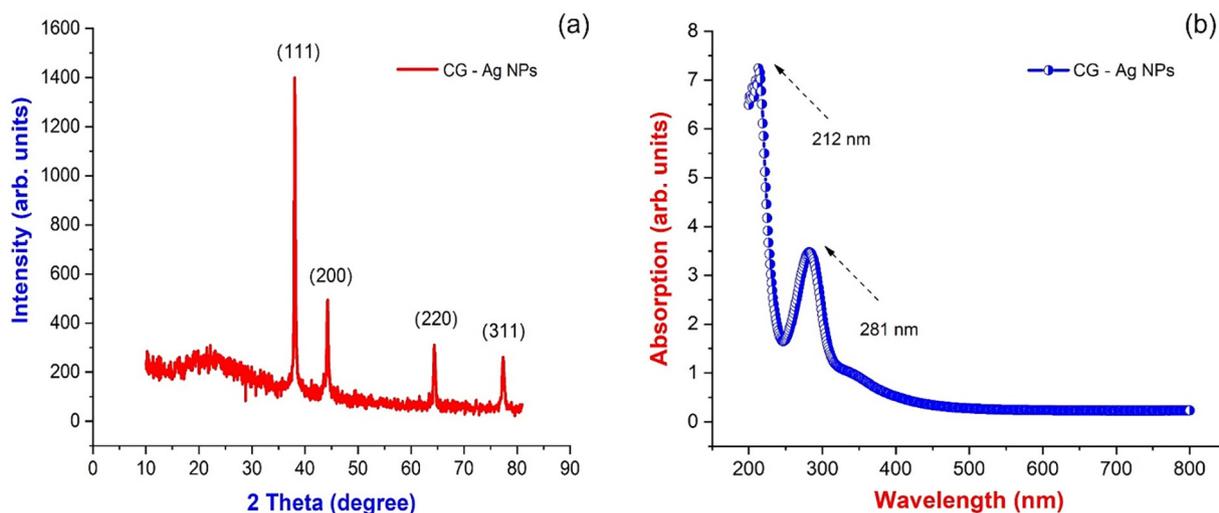


Fig. 2. (a) X-ray diffraction; (b) UV visible spectrum of *Couroupita guianensis* flower petal extract synthesized AgNPs.

observations as evident in the emergence of crystalline silver nanoparticles with cubic structures. The result of XRD agrees with earlier plant-based synthetic reports (Manimegalai et al., 2014). The Scherrer equation was used to calculate the average crystallite size of produced AgNPs, and the average crystallite size was determined to be 34 nm (Table 1). The existence of prominent crystalline peaks without any more impurity peaks has proven the emergence of pure crystalline silver nanoparticles.

### 3.2. UV-visible spectroscopy analysis

UV spectrum obtained from the synthesized sample of silver nanoparticles with the incorporation of petal extract of *Couroupita guianensis* is represented in Fig. 2(b). It reveals the traces of silver ions as evident of bio-reduction from silver oxide. It also could be visually observed with color variations in the solution combination from light blue to dusky brown after 30 min of the reaction process. Observed changes in solution color may be because of bilateral electromagnetic fields generated by coordinated oscillations of free electro heads in surface plasmon resonance (Joy Prabu et al., 2022). Spectral absorption of AgNPs depends mainly on the particle size, medium, and chemical environment. Hence, UV-vis spectroscopy analysis facilitates the identification of the reduction of silver ions while scanning in the wavelength range of 200 to 600 nm. It is known from the standards data that characteristic absorption of silver nanoparticles is found to be existing in the range around 212 and 281 nm as shown in Fig. 2(b).

### 3.3. FTIR analysis

Biosynthesis silver particles on the nanoscale are usually stabilized by phytochemical compounds through molecular interactions with metal surfaces. FTIR analysis can be used to explore the nature of the molecular interaction and its functionalities as reported in the literature based on the functional group reference

peaks. This analysis also could reveal the interaction between silver nitrate and boilers present in the flower extract from *Couroupita guianensis*. Fig. 3 shows the observed FTIR spectrum of the sample showing the peaks at wavenumbers  $3939\text{ cm}^{-1}$ ,  $3336\text{ cm}^{-1}$ ,  $3018\text{ cm}^{-1}$ ,  $2765\text{ cm}^{-1}$ ,  $2039\text{ cm}^{-1}$ ,  $1475\text{ cm}^{-1}$ ,  $969\text{ cm}^{-1}$ . All characteristic peaks evident the existence of silver nanoparticles from biosynthesis and the peaks corresponding to the molecules that can be involved in the synthesis and stabilization of silver nanoparticles. The absorption bands at  $3939\text{ cm}^{-1}$  parallel to the vibrations of O–H between the molecules (amines of phenolic and alcoholic compounds). The peaks in rang  $3336\text{ cm}^{-1}$  are among the flavones, triterpenoids, and polyphenols. Thus, the interaction between the ions of metals and the group of amides in the flake extract of *Couroupita guianensis* is involved in the synthesis and stabilization (capping) of the nanosilver formation, as previously described (Joy Prabu et al., 2022; Mythili et al., 2021). Peaks located at wavenumbers  $3018\text{ cm}^{-1}$  and  $2765\text{ cm}^{-1}$  represented groups of phenols, amines, and the presence of stretching alkanes. The absorption bands at  $2765\text{ cm}^{-1}$  and  $2039\text{ cm}^{-1}$  on the other hand, correspond to asymmetric and symmetric stretching of  $-\text{CH}_2$  and  $-\text{CH}$ , respectively. C–H aliphatic vibrations may be responsible for the absorption band at  $2039\text{ cm}^{-1}$ . The peak at  $1475\text{ cm}^{-1}$  investigates the vibrations C=O of  $-\text{COOH}$ . The carbon-carbon double bond C=C is responsible for the bands at  $1475\text{ cm}^{-1}$ . The C–N tensile aromatic amines are represented by the strong peaks at  $1074\text{ cm}^{-1}$  and  $969\text{ cm}^{-1}$ . The presence of amino ( $-\text{N}-\text{H}$ ) functional groups accounts for the absorbance at  $824\text{ cm}^{-1}$ . The  $767\text{ cm}^{-1}$  and  $668\text{ cm}^{-1}$  characteristic bands were identical to the alkane's groups discovered in the plant extract, which could alter nanoparticle production.


### 3.4. Scanning electron microscope (SEM) analysis & DLS analysis

Using an extract from the flower petals of *Couroupita guianensis*, the surface morphology images investigate the size and shape of the produced silver nanoparticles. The SEM characteristics of the

Table 1

Based on the XRD of AgNPs, a crystallite size estimate was made.

S. No	Pos. [ $2^\circ$ degree]	FWHM. [ $2^\circ$ degree]	d-spacing [Å]	Crystallite size
1	38.0421	0.2460	2.36545	35.69
2	44.2284	0.2952	2.04789	30.35
3	64.4014	0.2460	1.44672	39.88
4	77.3702	0.3444	1.23342	30.88

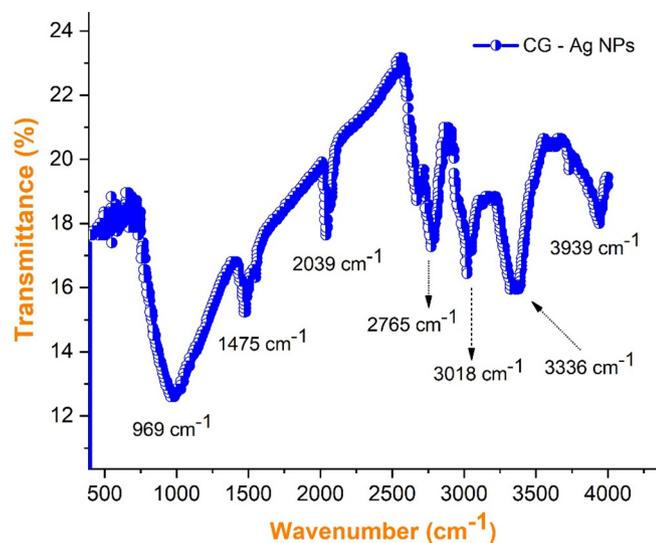


**Fig. 3.** FTIR spectra of synthesized AgNPs using flower petal extracts of *Couroupita guianensis*.

prepared nanoparticles Ag are found in Fig. 4(a-b). The SEM illustration exhibited a sponge-like structure of nanoparticles ranging up to 20 nm. The result of hydrodynamic size estimation of silver nanoparticles employed using DLS analysis is given in Fig. 4(c). It shows the average particle size distribution of silver nanoparticles

(diameter = 3.2 nm and Standard Deviation = 1.9  $\mu\text{m}$ ) is signified within the range of 3.2 nm as listed in (Table 2). It ensures the screening of small particles by larger phytochemicals of couroupita genesis attached to the surface of AgNPs (Manimegalai et al., 2014; Bauer et al., 1966).

### 3.5. Antibacterial activities

Although there are numerous analytical procedures for evaluating AgNPs' antibacterial activity, the standard and the most susceptible process is the plate diffusion method. Observed results of antibacterial activities of flake extract containing silver nanoparticles against Gram-positive (*B. Sublimus*) and Gram-negative (*E. Coli*) are shown in Fig. 5 with the zone of inhibition. AgNPs have strong inhibitory activity against Gram-positive bacterial species. For *Bacillus subtilis* (Table 3) a maximum inhibition zone is observed to be 16 mm. AgNPs have shown higher bactericidal activity in *Bacillus subtilis* compared to the negative *Escherichia coli* Gram. As reported in the literature, different mechanisms for the antibacterial activity of similar compounds from the flowers of croupier guianensis. The major bacteriological activity of the floral extract against bacterial species is mainly because of the existence of numerous antibacterial compounds, such as flavonoids, phenols, flavor compounds, isatin, and indiglumin. As reported in the literature, the antibacterial activity of identical extracts is possible from combinations of the croupier guianensis. The plants containing phenolic compounds are known well for their bio-related activities, such as antibacterial, fungicide, antibacterial, anti-mutagen, and anti-inflammatory drugs, which have been assigned

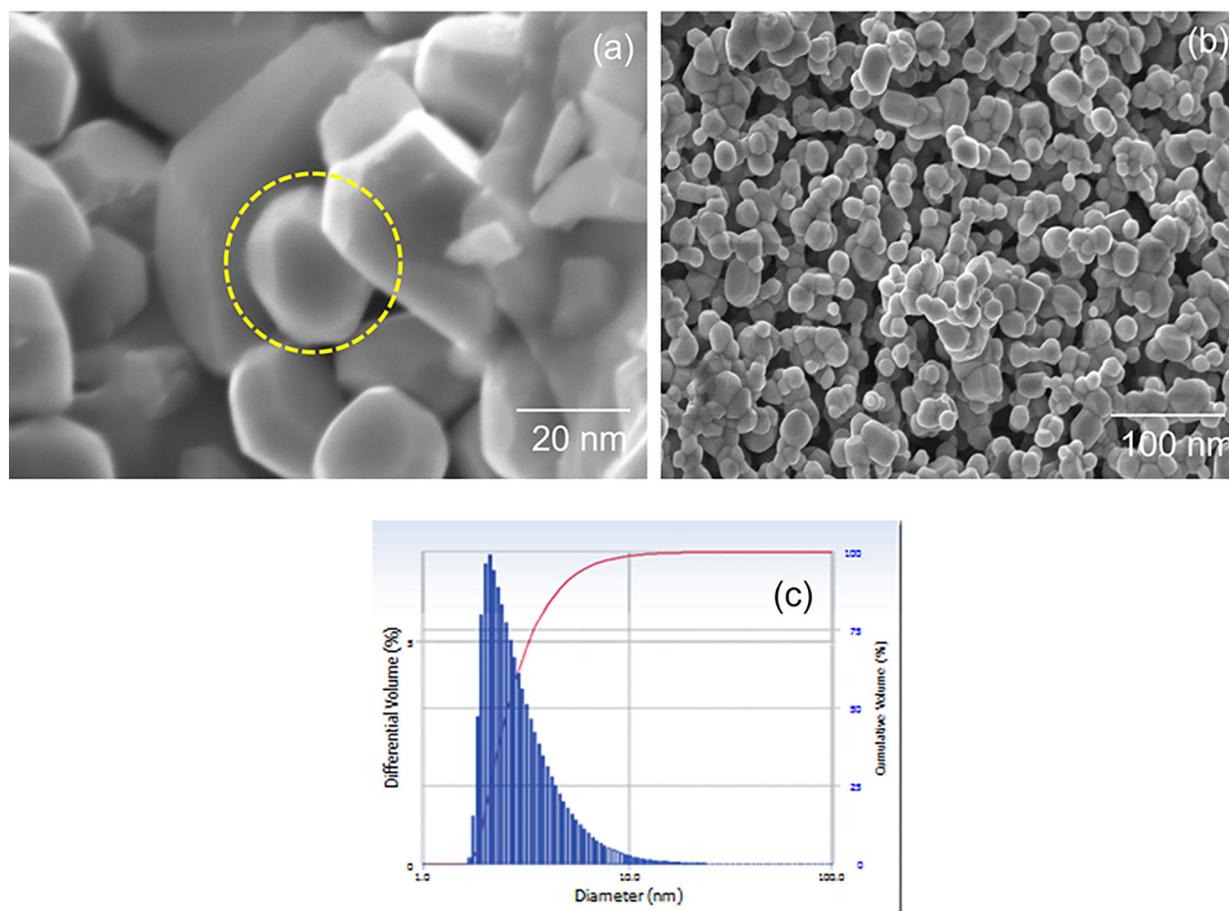

**Fig. 4.** (a-b). Scanning electron microscopy images of silver nanosponges synthesized from *Couroupita guianensis* flower petal extracts; (c) Dynamic Light Scattering of AgNPs using flower petal extracts of *Couroupita guianensis*.

**Table 2**

In order to determine the average particle size and distribution of nanoparticles, dynamic light scattering (DLS) was performed on AgNPs synthesized from flower petal extracts of *Couroupita guianensis*.

S. No	Peak	Diameter (nm)	Std. Dev.
1	1	3.2	1.9
2	2	0	0.0
3	3	0	0.0
4	4	0	0.0
5	5	0	0.0
Average		3.2	1.9

to their hydroxyl groups ( $-OH$ ) (Mani et al., 2021; Mani et al., 2021). Many aliphatic hydrocarbons, quercetin, and stigmainol from extracts of floral flakes, as mentioned earlier, also support antibacterial activity. Quinine is the main phenolic compound of a flower which leads to the loss and deactivation of its functions. In antibacterial activity, the most common targets are surface adhesion, cellular wall polypeptides, and membrane-related enzymes. Flazotide is known for the restriction of *B. subtilis* and *Escherichia* in respect of the class of flavonoids *E. Coli* by binding with ATP to the party. Induced DNA also increases the melting capacity of bacterial membranes and the loss of potential membranes. The antimicrobial action was responsible for the multiple and exhibited effects of the compounds in floral extracts (Nithiyavathi et al., 2021; Mani et al., 2021). The combined effect of a floral mixture and nano form can be explained by the increased proportion of surface to volume of the nanoparticles, which provides the largest contact area with bacteria (Perumal et al., 2022; Perumal et al., 2022).

### 3.6. Photocatalytic studies

Fig. 6(a) shows the absorption spectra of MB at regular intervals throughout the whole degradation reaction with CG-Ag nanoparticles. The CG-Ag NPs were then kept under visible light radiation at the start of the reaction with the fluid. 100 ml of methylene blue dye (MB) solution was swirled with 0.1 g of generated CG-Ag nanoparticles at a concentration of 5 ppm in a conventional photocatalytic dye degradation procedure. Before being exposed to visible light, the stable aqueous dye solution was agitated for 50 min. Every 50 min, the experiment was repeated, and the UV-vis absorption spectra were recorded. The experiment lasted 150 min (one cycle), with the absorption spectrum collected every

**Table 3**

Bacterial strains of Gram - positive and Gram - negative were tested for the zone of inhibition of AgNPs.

S. No.	Bacteria	Zone of Inhibition (mm in diameter)		
		Control	Stand*	Sample
1	<i>Bacillus subtilis</i>	-	16	16
2	<i>Escherichia coli</i>	-	16	14

50 min. In a probable graphic illustration of MB dye degradation, visible light irradiation produces an electron-hole ( $e^-/h^+$ ) pair between the conduction band and the valence band of CG-Ag nanoparticles. MB dye is degraded into less harmful organic solutions or minerals by the active oxygen species  $O_2$ ,  $O_2^{\bullet-}$ ,  $HOO^{\bullet}$ , and  $-OH$  (Brajesh et al., 2016; Mythili et al., 2021; Mani et al., 2021; Panimalar et al., 2022). The pseudo-first-order model was used to investigate the reaction kinetics of MB dye using Eq. (1).

$$\ln(C_t/C_0) = kt. \quad (1)$$

Where  $C_0$  is the initial dye concentration,  $C_t$  is the dye concentration after various irradiation durations, and 'k' is the photodegradation rate constant ( $\text{min}^{-1}$ ) [Perumal et al., 2023; Magdalane et al., 2021]. Using an Ag catalyst generated from a solution  $\sim$  pH 9 with a maximum degradation of about 84 % is shown in Fig. 6(b), the stability of CG-Ag NPs against MB dye in a five-cycle process is examined. The CG-Ag NPS catalyst was recycled five times from the preceding patch of the experiment in this experiment. In this study, the reaction rate constant was calculated using the equation. A graph of  $\ln(C_0/C)$  vs reaction time is shown in Fig. 7(a-b).

From photocatalytic investigations of CG-AgNPs, we discovered that the rate constant for varying doses of MB dye is in the range of  $0.0714-0.0592 \text{ min}^{-1}$ . The photocatalytic efficiencies of the catalyst may be reduced because of the following possible cause. Continuous dye adsorption on the catalyst surface can deplete the active sites, reducing photocatalytic activity. Furthermore, incident light penetration to the catalyst surface can be reduced by the surface adsorbed dye, impacting the production of electron-hole pairs (Lakshmanan et al., 2018; Kumar et al., 2011; Chandrasekar et al., 2022; George et al., 2022). This could explain why near the conclusion of the fifth cycle, the photodegradation efficiency of CG-Ag nanoparticles decreased. Fig. 7(c) depicts the reaction pathway that occurred during the photocatalytic activity of the CG-Ag

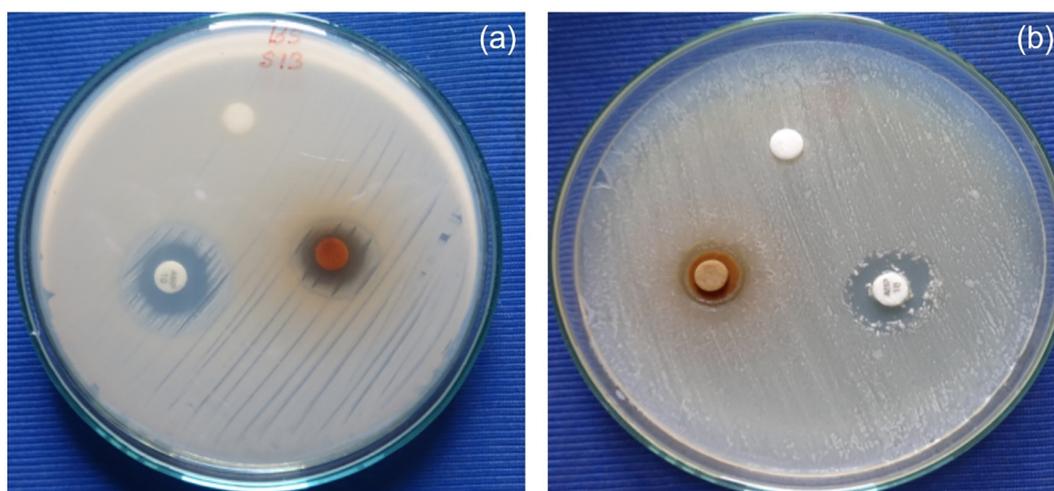


Fig. 5. (a-b). Antibacterial activity of AgNPs against Gram Positive (*Bacillus subtilis*) and Gram Negative (*Escherichia coli*) stains.

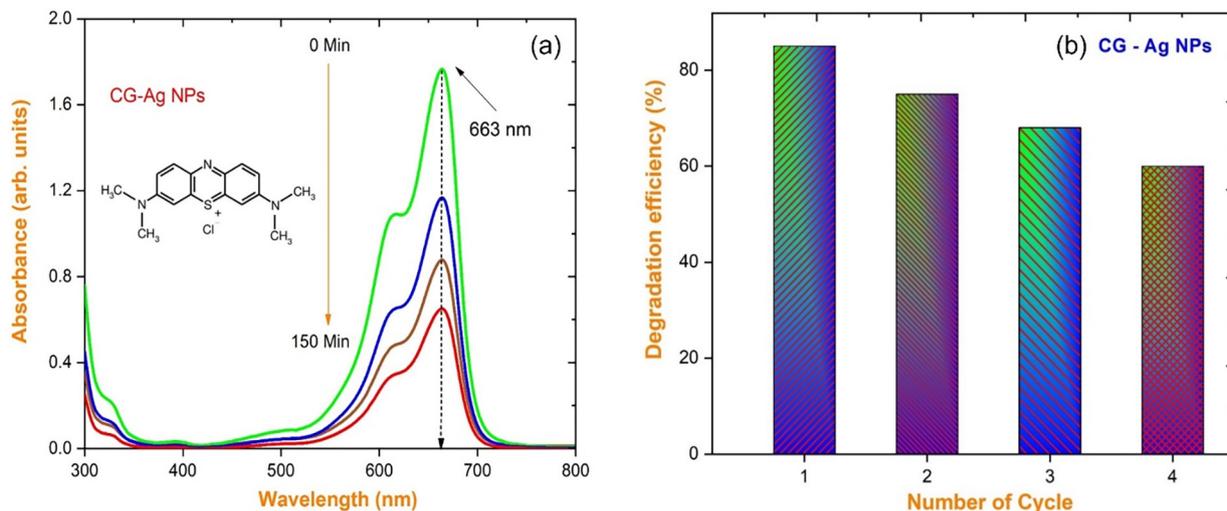


Fig. 6. (a) Time dependent UV-vis absorption spectra; (b) Photocatalytic degradation efficiency bar diagram of MB recorded in the existence of CG-Ag nanoparticles.

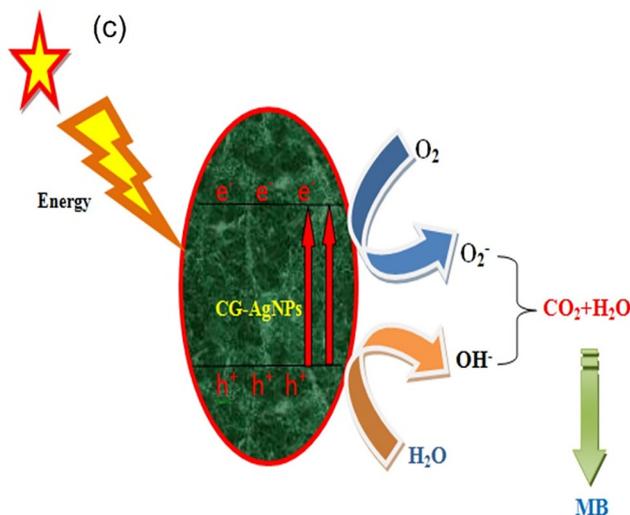
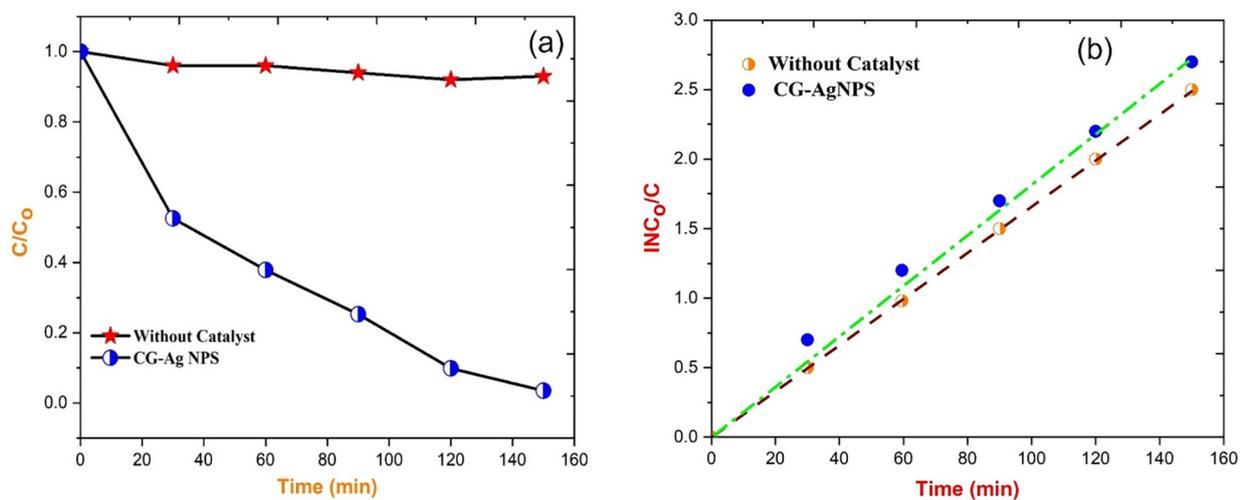


Fig. 7. (a) Photocatalytic degradation efficiency of C/C<sub>0</sub> vs time; (b) lnC<sub>0</sub>/C vs time; (c) proposed photocatalytic reaction mechanism of CG-AgNPs photocatalyst.

nanoparticles photocatalyst under visible light (Alhaji et al., 2019; Subash et al., 2022).

#### 4. Conclusion

The present work is an attempt at plant-mediated nanoparticle synthesis and its characterization. The current study revealed that the extracts of the flower petals from *Couroupita guianensis* can synthesize Ag NPs fast, ecologically, economically, and in a renewable way. The produced silver nanoparticles were discovered to be crystalline with a face-centered cubic (FCC) shape. The typical crystallite size is 34 nm. The morphology showed that nanoparticles with an average size of 32 nm have a trim dispersed flower shape, and the EDX validated the presence of elemental composition. The adequate reduction and stabilization of silver nanoparticles are due to phytochemicals, such as flavonoids, proteins, and phenolic compounds, which are produced in the extract of flower petals from *Couroupita guianensis*. Silver nanoparticles had remarkable antibacterial action against gram-positive bacteria when compared to Gram-negative bacteria (*Escherichia coli*) (*Bacillus subtilis*). The photocatalytic activity compared to CG-Ag NPs exhibited degradation of methylene blue dye. The degradation efficiency is found to be 90 % was witnessed on enhanced photocatalytic activity of CG-Ag NPs are suitable materials for environmental applications.

#### Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

#### Acknowledgements

The authors acknowledge management's efforts and express their gratitude. Also, authors thank the University of Douala, Cameroon for its support and encouragement.

#### Appendix A. Supplementary material

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.jksus.2022.102455>.

#### References

- Aarti, S., Sarita, K., Pushplata, T., 2017. A facile and rapid method for green synthesis of *Achyranthes aspera* stem extract-mediated silver nanocomposite with cidal potential against *Aedes aegypti* L. *Saudi Journal of Biological Sciences* 45, 54–62.
- Alexandra, C.B., Oana, G., Alexandru, M.G., Laurentiu, M., Anton, F., Ecateruan, A., 2018. Biomedical applications of silver nanoparticles: An up-to-date overview. *Nanomaterials* 8, 1–25.
- Alhaji, N.M.I., Nathiya, D., Kaviyarasu, K., Meshram, M., Ayeshamariam, A., 2019. A comparative study of structural and photocatalytic mechanism of AgGaO<sub>2</sub> nanocomposites for equilibrium and kinetics evaluation of adsorption parameters. *Surf. Interfaces* 17, 100375.
- Bauer, A.W., Kirby, W.M., Sherris, J.C., Turck, M., 1966. Antibiotic susceptibility testing by a standardized single disk method. *Am. J. Clin. Pathol.* 45 (4), 493–496.
- Brajesh, K., Kumari, S., Alexis, D., Luis, C., 2016. Extracellular green synthesis of silver nanoparticles using Amazonian fruit *Araza* (*Eugenia stipitata* MvVaugh). *Trans. Nonferrous Met. Soc. Chin.* 26, 2363–2371.
- Chandrasekar, M., Subash, M., Perumal, V., Panimalar, S., Aravindan, S., Uthrakumar, R., Inmozhi, C., Isaev, A.B., Muniyasamy, S., Raja, A., Kaviyarasu, K., 2022. Specific charge separation of Sn doped MgO nanoparticles for photocatalytic activity under UV light irradiation. *Sep. Purif. Technol.* 294, 121189.
- Fuad, A., Srinivasan, P., Selva, K.T., Nadhari, A.L., Almansob, A., Dawoud, T., Govarthanan, M., 2019. Photosynthesis of silver nanoparticles using *Mangifera indica* flower extract as reductant and their broad-spectrum antibacterial activity. *Bioorg. Chem.* 88, 5.
- George, A., Magimai, D., Raj, A., Venci, X., Dhayal Raj, A., Albert Irudayaraj, A., Josephine, R.L., John Sundaram, S., Al-Mohaimed, A.A., Al, D.A., Farraj, T.W.,

- Chen, 2022. Photocatalytic effect of CuO nanoparticles flower-like 3D nanostructures under visible light irradiation with the degradation of methylene blue (MB) dye for environmental application. *Environ. Res.* 203, 111880.
- Gousia, S.K., Ashok Kumar, A., Vinay Kumar, T., Naveena Lavanya Latha, J., 2013. Biological activities and medicinal properties of *Couroupita guianensis*. *International Journal of Pharmacy and Pharmaceutical science research* 3 (4), 140–143.
- Gupta, P., Nain, P., Sidana, J., 2012. Antimicrobial and antioxidant activity on *Emblicofficinalis* seed extract. *International Journal of research in Ayurveda and Pharmacy* 3 (4), 591–596.
- Joy Prabu, H., Varghese, R., Johnson, I., John Sundaram, S., Dhayal Raj, A., Rajagopal, R., Kuppusamy, P., Sathya, R., Kaviyarasu, K., 2022. Laser induced plant leaf extract mediated synthesis of CuO nanoparticles and its photocatalytic activity. *Environ. Res.* 212, 113295.
- Katta, V.K., Dubey, R.S., 2020. Green synthesis of silver nanoparticles using *Tagetes erecta* plant and investigation of their structural, optical, chemical and morphological properties. *Mater. Today: Proc.* 28, 18–27.
- Krishna, G., Singara, C.M., 2016. Synthesis of silver nanoparticles by chemical and biological methods and their antimicrobial properties. *J. Exp. Nanosci.* 11, 9–21.
- Kseniya, H., Alena, K., Viktoryia, K., Aliaksandr, K., Galina, N., Irina, K., Artem, K., Vladmir, A., 2020. Green approach for obtaining stable pectin-capped silver nanoparticles: Physico-chemical characterization and antibacterial activity. *Colloids and Surface A: Physicochemical and Engineering Aspects* 585, 124142.
- Kumar, C.S., Nares, G., Sudheer, V., Veldi, N., Anurag, A.E., 2011. A Short Review on Therapeutic Uses Of *Couroupita guianensis* Aubl. *Int. Res. J. Pharm. App. Sci.* 1, 105–108.
- Lakshmanan, G., Sathiyaseelan, A., Kalaihelvan, P.T., Mrugesan, K., 2018. Plant-mediated synthesis of silver nanoparticles using fruit extract of *Cleome viscosa* L: Assessment of their antibacterial and anticancer activity, *Karbala International Journal of Modern. Science* 4, 61–68.
- Logambal, S., Maheswari, C., Chandrasekar, S., Thilagavathi, T., Inmozhi, C., Panimalar, S., Bassyouni, F.A., Uthrakumar, R., Gawwad, M.R.A., Aljowaie, R.M., Al Farraj, D.A., Kanimozhi, K., 2022. Synthesis and characterizations of CuO nanoparticles using *Couroupita guianensis* extract for and antimicrobial applications. *Journal of King Saud University - Science* 34 (3), 101910.
- Magdalane, C.M., Priyadharsini, G.M.A., Kaviyarasu, K., Jothi, A.I., Simiyon, G.G., 2021. Synthesis and characterization of TiO<sub>2</sub> doped cobalt ferrite nanoparticles via microwave method: Investigation of photocatalytic performance of congo red degradation dye. *Surf. Interfaces* 25, 101296.
- Mani, M., Okla, M.K., Selvaraj, S., Ram Kumar, A., Kumaresan, S., Muthukumar, A., Kaviyarasu, K., El-Tayeb, M.A., Elbadawi, Y.B., Almaari, K.S., Ahmed Almunqedi, B.M., Elshikh, M.S., 2021. A novel biogenic Allium cepa leaf mediated silver nanoparticles for antimicrobial, antioxidant, and anticancer effects on MCF-7 cell line. *Environ. Res.* 198, 111199.
- Mani, M., Pavithra, S., Mohanraj, K., Kumaresan, S., Alotaibi, S.S., Eraqi, M.M., Gandhi, A.D., Babujanarthanam, R., Maaza, M., Kaviyarasu, K., 2021. Studies on the spectrometric analysis of metallic silver nanoparticles (Ag NPs) using *Basella alba* leaf for the antibacterial activities. *Environ. Res.* 199, 111274.
- Mani, M., Harikrishnan, R., Purushothaman, P., Pavithra, S., Rajkumar, P., Kumaresan, S., Al, D.A., Farraj, M.S., Elshikh, B., Balasubramanian, K.K., 2021. Systematic green synthesis of silver oxide nanoparticles for antimicrobial activity. *Environ. Res.* 202, 111627.
- Manimegalai, S., Sridharan, T.B., Rameshpathy, M., Rajeswari, D., 2014. Antioxidant, phytochemical screening and antimicrobial activity of *Couroupita Guianensis* flower extract. *Der Pharmacia letter* 6 (6), 251–256.
- Mythili, R., Srinivasan, P., Praburaman, L., Mysoon, M., Al-Ansari, D., Latifah Al-Humaid, K., Vijayalakshmi, S., Selvankumar, T., 2021. Biogenic production of silver nanoparticles from the milk of *Capra aegagrus hircus* and mechanism of antibacterial activity on different bacteria. *Applied. Nanoscience*.
- Nayanmoni, G., Punuri Jayase, K.B., Chandan, M., Utpal, B., 2015. Green synthesis and characterization of silver nanoparticles using alcoholic flower extract of *Nyctanthes arbortristis* and in vitro investigation of their antibacterial and cytotoxic activities. *Material science and Engineering* 46, 463–469.
- Nithiyavathi, R., John Sundaram, S., Theophil Anand, G., Raj Kumar, D., Dhayal Raj, A., Al Farraj, D.A., Aljowaie, R.M., AbdelGawwad, M.R., Samson, Y., Kaviyarasu, K., 2021. Gum mediated synthesis and characterization of CuO nanoparticles towards infectious disease-causing antimicrobial resistance microbial pathogens. *J. Infect. Public Health* 14 (12), 1893–1902.
- Panimalar, S., Uthrakumar, R., Tamil Selvi, E., Gomathy, P., Inmozhi, C., Kaviyarasu, K., Kennedy, J., 2020. Studies of MnO<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterostructure efficient of visible light photocatalyst for pollutants degradation by sol-gel technique. *Surf. Interfaces* 20, 100512.
- Panimalar, S., Subash, M., Chandrasekar, M., Uthrakumar, R., Inmozhi, C., Al-Onazi, W.A., Al-Mohaimed, A.M., Tse-Wei Chen, J., Kennedy, M., Maaza, K.K., 2022. Reproducibility and long-term stability of Sn doped MnO<sub>2</sub> nanostructures: Practical photocatalytic systems and wastewater treatment applications. *Chemosphere* 293, 133646.
- Panimalar, S., Logambal, S., Thambidurai, R., Inmozhi, C., Uthrakumar, R., Muthukumar, A., Rasheed, A., Gatasheh, K., Mansour, K., Raja, A., Kennedy, J., Kaviyarasu, K., 2022. Effect of Ag-doped MnO<sub>2</sub> nanostructures suitable for wastewater treatment and other environmental pollutant applications. *Environ. Res.* 205, 112560.
- Periasamy, A., Subash, C.B., Hyun, S.Y., Choul Gyun, L., 2019. Temperature - dependent green biosynthesis and characterization of silver nanoparticles using

- balloon flower plants and their antibacterial potential. *J. Mol. Struct.* 1177, 302–309.
- Perumal, V., Sabarinathan, A., Chandrasekar, M., Subash, M., Inmozhi, C., Uthrakumar, R., Isaev, A.B., Raja, A., Elshikh, M.S., Almutairi, S.M., Kaviyarasu, K., 2022. Hierarchical nanorods of graphene oxide decorated SnO<sub>2</sub> with high photocatalytic performance for energy conversion applications. *Fuel* 324, 124599.
- Perumal, V., Inmozhi, C., Uthrakumar, R., Robert, R., Chandrasekar, M., Beer Mohamed, S., Shehla Honey, A., Raja, F.h.A., Al-Mekhlafi, K.K., 2022. Enhancing the photocatalytic performance of surface - Treated SnO<sub>2</sub> hierarchical nanorods against methylene blue dye under solar irradiation and biological degradation. *Environ. Res.* 209, 112821.
- Perumal, V., Uthrakumar, R., Chinnathambi, M., Inmozhi, C., Robert, R., Rajasaravanan, M.E., Raja, A., Kaviyarasu, K., 2023. Electron-hole recombination effect of SnO<sub>2</sub>-CuO nanocomposite for improving methylene blue photocatalytic activity in wastewater treatment under visible light. *J. King Saud Univ. Sci* 35, 102388.
- Renuka, R., Devi, R., Sivakami, M., Thilagavathi, T., Uthrakumar, R., Kaviyarasu, K., 2020. Biosynthesis of silver nanoparticles using *Phyllanthus Emblica* fruit extract for antimicrobial application. *Biocatalysis and Agriculture Biotechnology* 24, 101567.
- Saddaf, R., Mohammad, A., Shabaz, A.K., Mohammad, S., Raffiq, A., 2019. Characterization, and synergistic antibacterial potential of green synthesized silver nanoparticles using aqueous root extracts of important medicinal plants of Pakistan. *Colloids Surf. B Biointerfaces* 179, 317–325.
- Senthil, M.T., Nagarajan, R., Suchartseingchin, A., Varada Rajulu, N., Nadir, A., 2019. Influence of silver nanoparticles on the mechanical, thermal, and antimicrobial properties of cellulose-based hybrid nanocomposite. *Composite part B: Engineering* 165, 516–525.
- Shangpeng, L., Jianwei, M., Wang, S., Shaojuan, C., Bin, W., 2019. Li, Jiwei, Silver nanoparticles incorporated Chitosan/calcium pyrophosphate hybrid micro flowers for antibacterial applications. *Mater. Lett.* 255, 126570.
- Subash, M., Chandrasekar, M., Panimalar, S., Inmozhi, C., Parasuraman, K., Uthrakumar, R., Kaviyarasu, K., 2022. Pseudo-first kinetics model of copper doping on the structural, magnetic, and photocatalytic activity of magnesium oxide nanoparticles for energy application. *Biomass Conv. Bioref.* 12, 1–11.
- Tatiane, M.P., Vera, L.P., Marcelo, H.S., Luciano, P., 2020. Modulating physical, chemical, and biological properties of silver nanoparticles obtained by green synthesis using different parts of the tree *Handroanthusheptaphyllus* (vell). *Colloid Interface Sci. Commun.* 32, 100224.
- Vijay, K., Simranjeet, S., Bhavana, S., Ragini, B., Ravindra, S., 2019. Green synthesis of silver nanoparticles using leaf extract of *Holopteleaintegrifolia* and preliminary investigation of its antioxidant, anti-inflammatory, antidiabetic and antibacterial activities. *J. Environ. Chem. Eng.* 7, 103094.
- Wong, K.C., Tie, D., 1995. Couroupita flowers yield an aliphatic hydrocarbon and stigmaterol, alkaloids, phenolics, and flavonoids and have the active principles isatin and indirubin (vital to its antimicrobial activity). *J. Essent. Oil Res.* 7, 225–227.